



FLEXIDECK® P-PD

A 56 Dry Mils, Fast Curing, Seamless, Vehicular Traffic Deck Coating for Exterior Concrete

1.01 DESCRIPTION

Flexideck® P-PD is a liquid applied, fast cure, high solids, water-catalyzed polyurethane, waterproof vehicular traffic deck system.

The system utilizes a primer, one coat of a water catalyzed, urethane basecoat, one coat of an aromatic urethane intermediate coat and one coat of an aromatic or optional aliphatic urethane topcoat. Flexideck® P-PD can be applied to protect surfaces against spalling, freeze-thaw damage, and chemicals commonly encountered on these surfaces. It is an elastomeric system designed to expand and contract with normal structural movements. It will not soften in heat nor become brittle in cold. Flexideck® P-PD is a proven waterproofing system primarily used on plywood, concrete and metal surfaces. Installed and maintained properly, Flexideck® P-PD Decking System will ensure years of service. Be sure to use the right product grade that complies with VOC regulations as per federal, state, statutory bodies, county and city regulations/codes at the place of installation of product.

1.02 FEATURES

- Seamless
- Elastomeric
- Non gassing
- Meets California VOC and SCAQMD Requirements
- Recoatable
- Good weatherability
- Fast curing

1.03 TYPICAL USES

- Vehicular Traffic Decks
- Over Occupied Space
- Roof Decks

1.04 PRODUCTS & PACKAGING

Enviro-Grip™ EP#1

3-gallon kit: One 3.5 gallon pail containing net 2 gallons (7.57 liters) of Side-A blue liquid and 1 gallons (3.78 liters) can of Side-B yellow liquid

15-gallon kit: Two 5 gallon (18.9 liters) pails of Side-A blue liquid, each containing 5 gallons and one 5 gallons pail of Side-B yellow liquid, containing 5 gallons (18.9 liters)

Enviro-Grip™ EP#2

2-quart kit: One quart (0.946 liter) can of Side-A black liquid, and one quart (0.946 liter) can of Side-B white liquid

2-gallon kit: One gallon (3.78 liter) can of Side-A black liquid, and one gallon (3.78 liter) can of Side-B white liquid

10-gallon kit: one 5 gallon (18.9 liter) pail of Side-A black liquid, and one 5 gallon (18.9 liter) pail of Side-B white liquid

Enviro-Grip™ PUR#555

2-gallon kit: 1 gallon (3.78 liters) can of Side-A blue liquid and 1 gallon (3.78 liters) can of Side-B yellow liquid

10-gallon kit: 1 5-gallon (18.9 liters) pail of Side-A blue liquid and 1 5-gallon (18.9 liters) pail of Side-B yellow liquid

P-Tuff® Classic

1 gallon (3.78 liter) can with a partial vial of catalyst

5 gallon (18.9 liter) pail with a full vial of catalyst

Topshield® 500

1 gallon (3.78 liter) can with vial of catalyst

5 gallon (18.9 liter) pail with 1/2 pint (0.24 liter) can of catalyst
55 gallon drum, net fill 50 gallons (189 liters) with 2 1/2 quart (2.36 liters) can of catalyst

Topshield® 5600EF

4.4-gallon kit: One 5 gallons (net 4 gallons, 15.1 liters) pail of Side-A and one 1/2 gallon (net 0.4 gallon, 1.5 liters) jar of Side-B

1.05 PRODUCT INSTRUCTION

- For complete information associated with the application of Flexideck® P-PD, refer to the General & Safety Guidelines section of the Poly-Tuff Systems International (PSI) catalog which describes the surface preparation, job conditions, finishing details and other necessary information.
- All products/materials to be used on this system should be purchased from PSI or its distributors or approved by PSI. For details on individual product, please refer to Product Data Sheet.
- For project specific recommendations, please contact PSI.
- Refer to Products Data Sheets for products referred in the System Specifications.

APPLICATION

2.01 SURFACE PREPARATION

- A. Check area of application to ensure that it conforms to the substrate requirements, as stated in the general guidelines section. Concrete surfaces require a medium sandpaper finish equal to or greater than an ICRI CSP #3. Surface preparation may be completed by shotblasting or the use of Poly-Tuff Profile and Etch cleaner. Peel and adhesion tests are recommended.
- B. Install a 100-200 sqft (9.30-18.58 sqm) mock up of the system to be installed and approve for aesthetics, color, texture, actual coverage rates and functionality before proceeding.
- C. For project specific recommendations, please contact PSI.

2.02 REPAIRS, CRACKS, JOINTS & FLASHING

- A. Apply a single or two component non-gassing polyurethane sealant over all joints, cracks and flashing.
- B. Bridge the joints, cracks, and flashings with 4" (10 cm) Polyester tape pushing it into the 30 mils (762 microns) pre-stripe of base coat. Alternatively, joints and cracks 1/16" (0.15 cm) or larger may be sealed flush with PTS E-101 concealed with 4" (10 cm) Super Seal Tape (concrete must be primed first and allow to dry).
- C. Over reinforcement tape, apply a pre-stripe coat of P-Tuff® Classic material and taper it onto the adjacent surface. Alternatively, no crack chasing or pre-stripe is necessary with the use of Super Seal Tape over a primed surface (see Super Seal Tape Data Sheet).
- D. Allow the surface to cure for 1 to 2 hours.

2.03 PRIMING

- A. Prime surface with Enviro-Grip™ EP#1, EP#2, or PUR#555 at a rate of 1 gallon/300 sqft (0.14 liters/m²) or 300 sqft/gallon. Apply using a brush or phenolic-core roller. This will result in 3 dry mils (76 microns) of coating. Existing urethane coated surfaces should be primed with Enviro-Grip™ PUR#555. Rough and pin-holed concrete surfaces may require more primer. Discovery of these issues is generally revealed in the mock up. See the Tech-Note Section of the PSI website. Do not allow primer to puddle, dry roll excess primer with a dry nap roller to pick up excess primer in puddles and overlaps.

2.04 COATING APPLICATION

- A. Apply P-Tuff® Classic mixed material to substrate at a rate of 2 gallons/100 sqft (0.80 liters/m²) or 50 sqft/gallon. P-Tuff® Classic mixed material or water-catalyzed mixed P-Tuff® Classic is a properly homogeneous mixed mixture of four parts of P-Tuff® Classic and one part of water by volume. Application will require more or less material depending on substrate conditions.
- B. Use a notched trowel or squeegee to spread P-Tuff® Classic mixed material evenly over the entire deck resulting in a minimum 24 ± 2 dry mils (609 ± 50 microns) thick membrane.
- C. When P-Tuff® Classic mixed material begins to gel, approximately 15 minutes after placement, broadcast 14-30 mesh rubber granules into the wet membrane to refusal. Normal usage is 20 lbs of rubber granules /100 sqft (0.98 kg/m²). Two top coats are required when utilizing rubber aggregates. Each top coat should be applied at a minimum of 100 sqft /gallon.
- D. When broadcasting silica sand, allow membrane to thicken to a firm and sticky surface (approximately 30-45 min) when the sand will adhere but not sink into the base coat. The aggregate should be dry, washed, and rounded silica sand in the, 12-20 (0.84-1.68mm), 16-30 (0.595-1.19mm) or 20-40 (0.84-1.62mm) mesh size (as required by customer specifications or as specified in systems specifications) and a 6.5 Mohs scale minimum hardness. Time for thickening to a firm sticky condition is dependent on atmospheric environments especially temperature and humidity. Allow coating to cure 2-4 hours before proceeding to subsequent coats.
- E. When P-Tuff® Classic is stiff enough to support weight without imprinting or denting the coating or, when coating is dry (approximately 2-3 hours at 70°F (21°C) and 50% relative humidity). Remove all loose aggregate by sweeping, vacuum or blowing the excess sand off the deck. Make any touch up or repairs. Allow repairs to cure.

2.05 INTERMEDIATE COAT APPLICATION

- A. Apply desired color of Topshield® 500 or Topshield® 5600EF at a rate of 1 1/4 gallon/100 sqft (0.51 liters/m²) or 80 sq/ft/gallon. This coat will result in an additional 18



SYSTEM SPECIFICATIONS

SECTION 2.3.2

± 2 dry mils (457 ± 50 microns) thick coating. Refer to the chart at the end of this System Description for coverage rates. Broadcast additional aggregate as needed via the "rain method" to cover any bare or insufficient aggregate placement.

- B. Check that no pinholing has occurred from concrete out gassing.
- C. At 70°F (21°C) and 50% relative humidity allow a minimum of 16 and a maximum of 48 hours for topcoat to cure before allowing vehicular traffic.

2.06 TOPCOAT APPLICATION

- A. Apply desired color of Topshield® 500 or Topshield® 5600EF at a rate of 1 gallon/100 sqft (0.41 liters/m²) or 100 sqft/gallon. This coat will result in an additional 11 ± 2 dry mils (279 ± 50 microns) thick coating. Broadcast additional aggregate as needed to cover any bare or insufficient aggregate placement. When using a color pack system, "boxing" from one mixed pail to the next is recommended. Always save 1 gallon or more and mix into the next pail to prevent color variation. Likewise, with pre-tinted topcoats, mix the last gallon or two from the previous batch into the new batch number. Box the last gallons of the last used batch numbers with the new batch number to prevent hue or shading variation.
- B. At 70°F (21°C) and 50% relative humidity allow a minimum of 16 and a maximum of 48 hours for topcoat to cure.

2.07 RAMPS, TURN RADII APPLICATION

- A. Over ramps, turn radii, and other heavy traffic areas only, apply an additional desired color of Topshield® 500 or Topshield® 5600EF at a rate of 1 gallon/100 sqft (0.4 liters/m²) or 100 sqft/gallon. Refer to the chart at the end of this System Description for coverage rates. This coat will result in an additional 11 ± 2 dry mils. (279 ± 50 microns) thick coating. Broadcast additional aggregate as needed to cover any bare or insufficient aggregate placement.
- B. At 70°F (21°C) and 50% relative humidity allow a minimum of 16 and a maximum of 48 hours for topcoat to cure.

2.08 FINISHED SYSTEM

- A. When applied as directed above, Flexideck® P-PD Vehicular Traffic Decking System will provide minimum 56 ± 5 dry mils (1422 ± 125 dry microns) with single topcoat, exclusive of aggregate, of superior waterproofing protection. Coverage rates and cure times will vary depending on temperature, relative humidity, surface roughness and porosity, aggregate selection and embedment, and application technique. Coverage rates provided are optimal and are not guaranteed.
- B. Material mil thickness rates are calculated on the theoretical coverage for smooth substrate and do not account for the actual texture or substrate conditions in the field or at the time of application. Sample mock ups on the projects are recommended to determine the exact coverage rates necessary to waterproof the deck and acceptable standards. Imperfections, spalling, scalling, rough surfaces, potholes, slope correction and other irregular textured surfaces may be filled in with P-Tuff® Classic Sand or Rubber Slurry and are estimated outside the stated minimum coverage rates reflected on Product Data Sheets.

2.09 LIMITATIONS

- A. **Concrete:**

The following conditions must not be coated with PSI deck coating systems or products: on grade or below grade slabs, split slabs with buried membrane, sandwich slabs with insulation, slabs over unvented metal pan, suspended pool, swimming pool decks without the use of Enviro-Grip™ 404FC primer and asphalt surfaces, asphalt overlays without the express written consent of PSI. PSI Deck Coating is not recommended over magnesite, gypsum lightweight and where chained or studded tires may be used.

 1. Concrete must exhibit 3000 psi minimum strength. An ICRI CSP 3 surface or greater is required for concrete surfaces to be coated.
 2. New concrete must be cured for 28 days unless otherwise approved by PSI in writing. New surfaces to be coated must be trowel finished in compliance with the American Concrete Institute (except that hand troweling is not required), followed by a fine hair brooming, left free of loose particles, and shall be without ridges, projections, voids and concrete droppings that would be mechanically detrimental to coating application or function. Light

broom finished concrete should be power washed before coating application.

3. Concrete cleaning see General & Safety Guidelines.

4. Surface preparation may be completed by shotblasting or the use of Poly-Tuff Profile and Etch cleaner. Peel and adhesion tests are recommended.

B. Plywood:

1. The only acceptable grade of plywood is APA rated exterior grade or better.

2. The appearance characteristics of the panel grade should be considered.

3. Plywood should be new or cleaned and sanded (see General & Safety Guidelines).

C. PSI Decking Systems will not withstand rising water tables or hydrostatic pressure on slab-on-grade decks.

D. Uncured materials are sensitive to heat and moisture.

E. A continuous coating application should ensure a deck with no lines or streaks.

F. The substrate must be structurally sound and sloped for proper drainage.

G. PSI assumes no liability for substrate defects.

2.10 JOB COMPLETION

A. Equipment should be cleaned with a urethane grade, environmentally-safe solvent, as permitted under local regulations, immediately after use.

B. Field visits by PSI personnel are for the purpose of making technical recommendations only and are not to supervise or provide quality control on the job site.

WARNING: The products in this system contain solvent, isocyanates, Epoxy Resin, and curatives.




SYSTEM SPECIFICATIONS

SECTION 2.3.2

COVERAGE RATE CHART

Primer: Enviro-Grip™ EP#1, #2, PUR#555	Basecoat: P-Tuff® Classic	Intermediate: Topshield® 500 or 5600EF	Topcoat: Topshield® 500 or 5600EF
	Mixed Material		1st Coat
1 gallon/300 sqft (0.14 liters/m ²)	2 gallons/100 sqft (0.8 liters/m ²)	1 1/4 gallons/100 sqft (0.51 liters/m ²)	1 gallon/100 sqft (0.41 liters/m ²)
300 sqft/gallon	50 sqft/gallon	80 sqft/gallon	100 sqft/gallon
			2nd Coat, Ramps, Turn Radii:
			1 gallon/100 sqft (0.41 liters/m ²)
			100 sqft/gallon

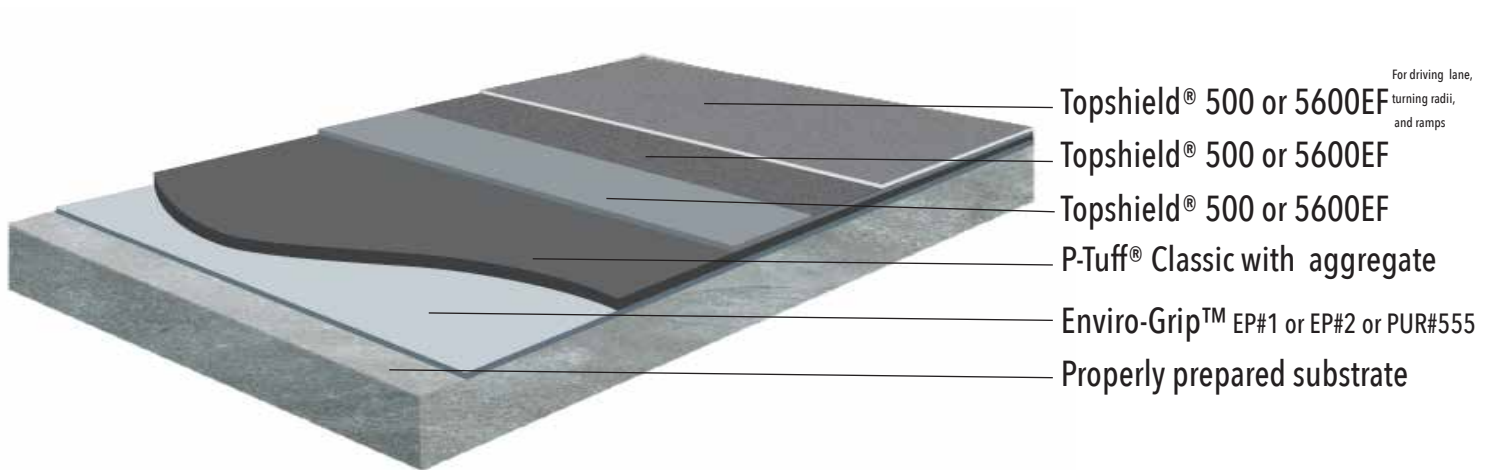

Please read all information in the General & Safety Guidelines, Product Data Sheets, Guide Specifications and Safety Data Sheets (SDS) before applying material. PSI Products are for "Professional Use Only" and preferably applied by professionals who have prior experience with the PSI Products or have undergone training in application of PSI Products. Published technical data and instructions are subject to change without notice. Contact your local PSI representative or visit our website for current technical data, instructions, and project specific recommendations.

LIMITED WARRANTY

PSI warrants its products to be free of manufacturing defects and that they will meet PSI current published physical properties. PSI warrants that its products, when properly installed by a state licensed waterproofing contractor according to PSI guide specifications and product data sheets over a sound, properly prepared substrate, will not allow water migration for a period of 12 months. Seller's sole responsibility shall be to replace that portion of the product which proves to be defective. There are no other warranties by PSI of any nature whatsoever expressed or implied, including any warranty of merchantability or fitness for a particular purpose in connection with this product. PSI shall not be liable for damages of any sort, including remote or consequential damages resulting from any claimed breach of any warranty whether expressed or implied. PSI shall not be responsible for use of this product in a manner to infringe on any patent held by others. In addition, no warranty or guarantee is being issued with respect to appearance, color, fading, chalking, staining, shrinkage, peeling, normal wear and tear or improper application by the applicator. Damage caused by abuse, neglect and lack of proper maintenance, acts of nature and/or physical movement of the substrate or structural defects are also excluded from the limited warranty. PSI reserves the right to conduct performance tests on any material claimed to be defective prior to any repairs by owner, general contractor, or applicator.

DISCLAIMER

All guidelines, recommendations, statements, and technical data contained herein are based on information and tests we believe to be reliable and correct, but accuracy and completeness of said tests are not guaranteed and are not to be construed as a warranty, either expressed or implied. It is the users responsibility to satisfy himself, by his own information and test, to determine suitability of the product for his own intended use, application and job situation and user assumes all risk and liability resulting from his use of the product. We do not suggest or guarantee that any hazard listed herein are the only ones which may exist. Neither seller nor manufacturer shall be liable to the buyer or any third person for any injury, loss or damage directly or indirectly resulting from use of, or inability to use, the product. Recommendations or statements, whether in writing or oral, other than those contained herein shall not be binding upon the manufacturer, unless in writing and signed by a corporate officer of the manufacturer. Technical and application information is provided for the purpose of establishing a general profile of the material and proper application procedures. Test performance results were obtained in a controlled environment and PSI makes no claim that these tests or any other tests, accurately represent all environments.